


Fe/Cr superlattices / GMR



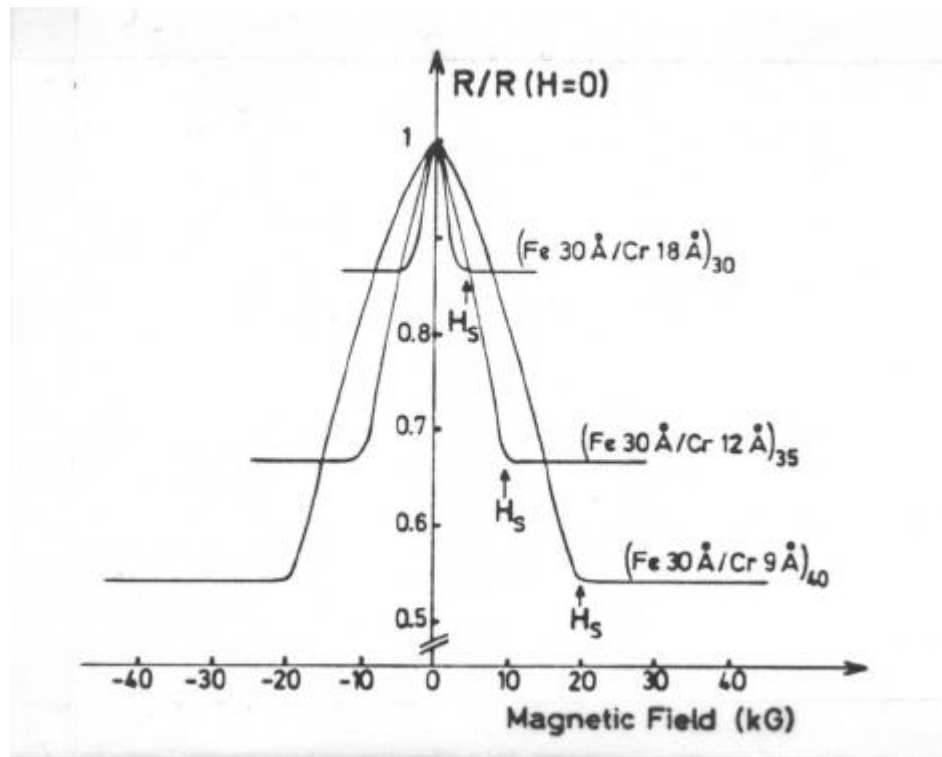


M.N. Baibich et al., PRL 61, 2472 (1988)

Fe/Cr superlattices / GMR

5 VB 6 VIB 7 VIIB 8 9 VIII





V 23	Cr 24	Mn 25	Fe 26	Co 27
50.9415	51.9961	54.93805	55.847	58.9332
1.6 5+	1.6 3+	1.5 2+	1.8 3+	1.8 2+
Vanadium	Chromium	Manganese	Iron	Cobalt

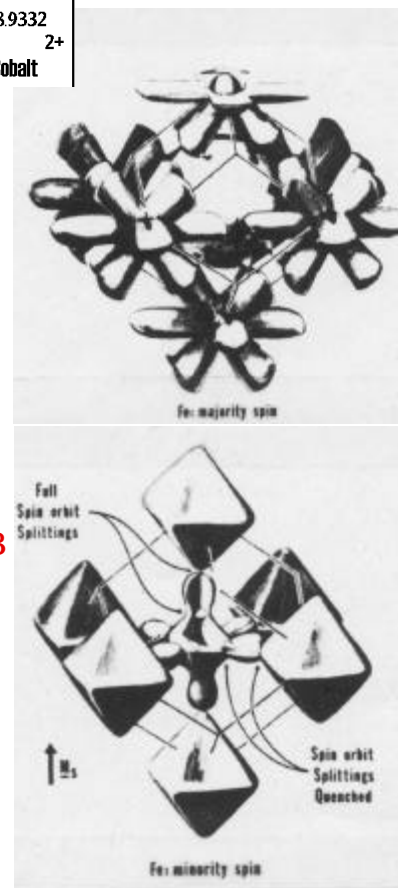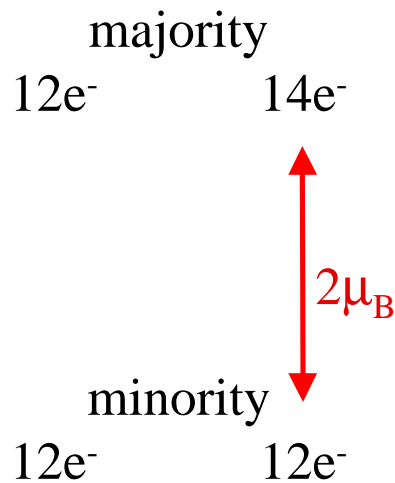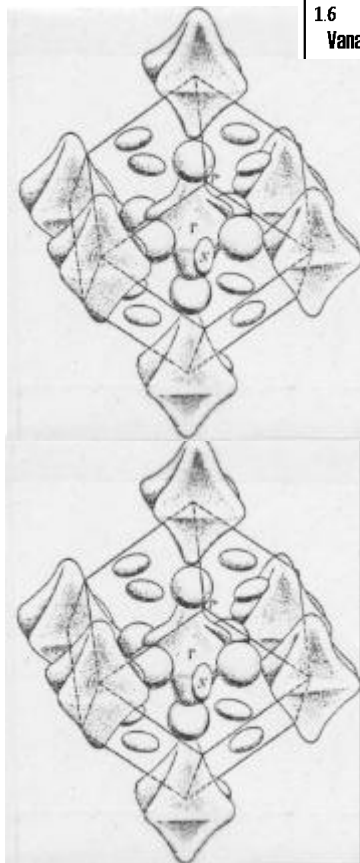

Ferromagnetic materials, E.P. Wohlfarth, North-Holland, Amsterdam (1980)


The Fermi Surfaces, A.P. Crackwell, K.C. Wong, Clarendon Press, Oxford (1973)

Fe/Cr superlattices / GMR

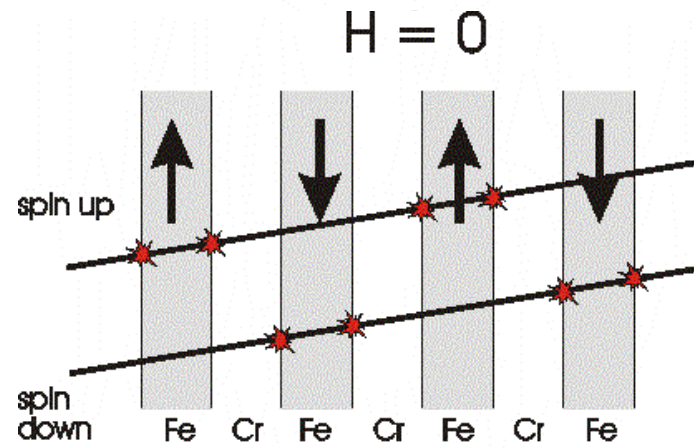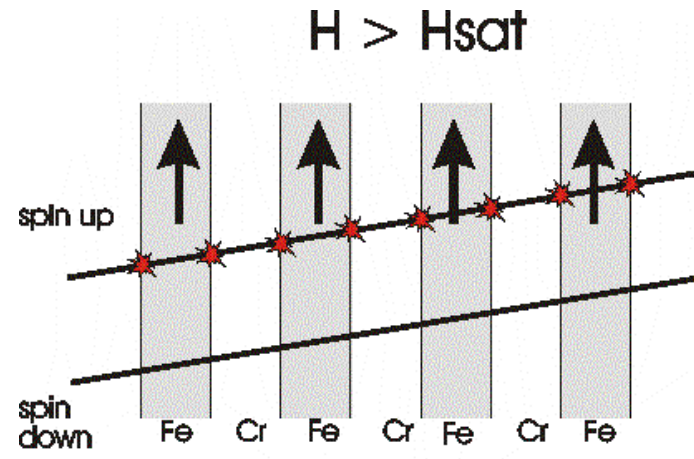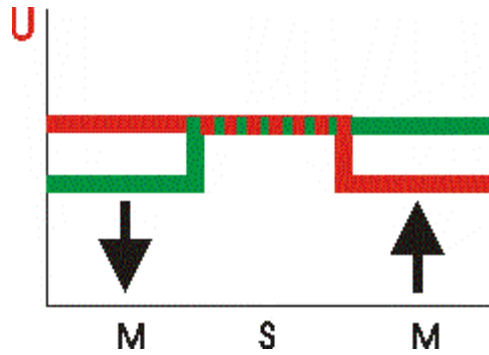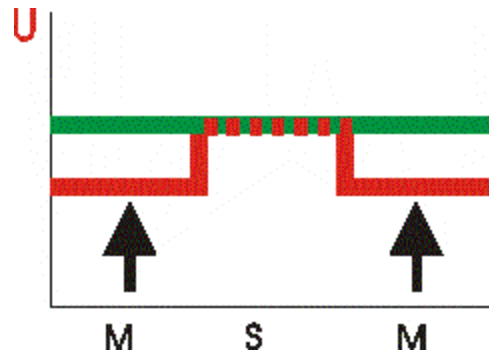

$r = \text{high}$


Epitaxial Fe/Cr layers on MgO(001) thickness dependence of resistivity

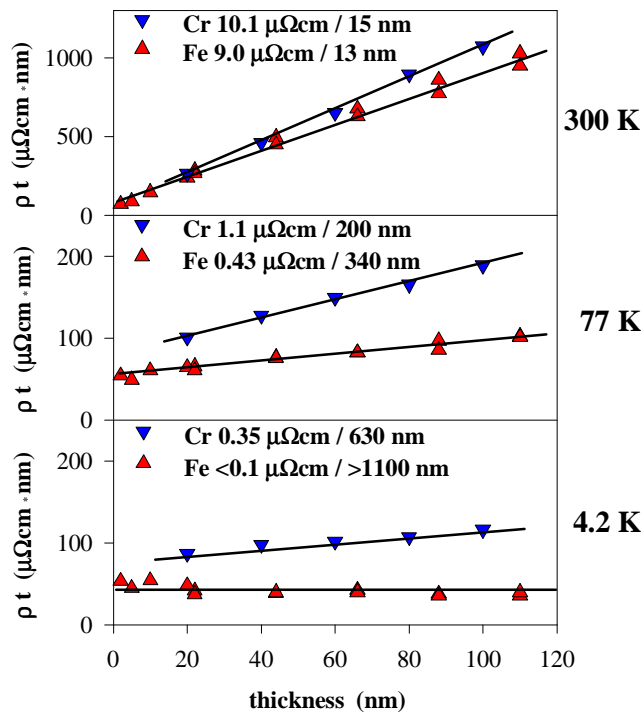

Negligible bulk defect density =>
only interface scattering



R. Schad, P. Beliën, G. Verbanck, V.V. Moshchalkov, Y. Bruynseraede
J. Phys. Condensed Matter 10, 6643 (1998)

INTERFACE ROUGHNESS

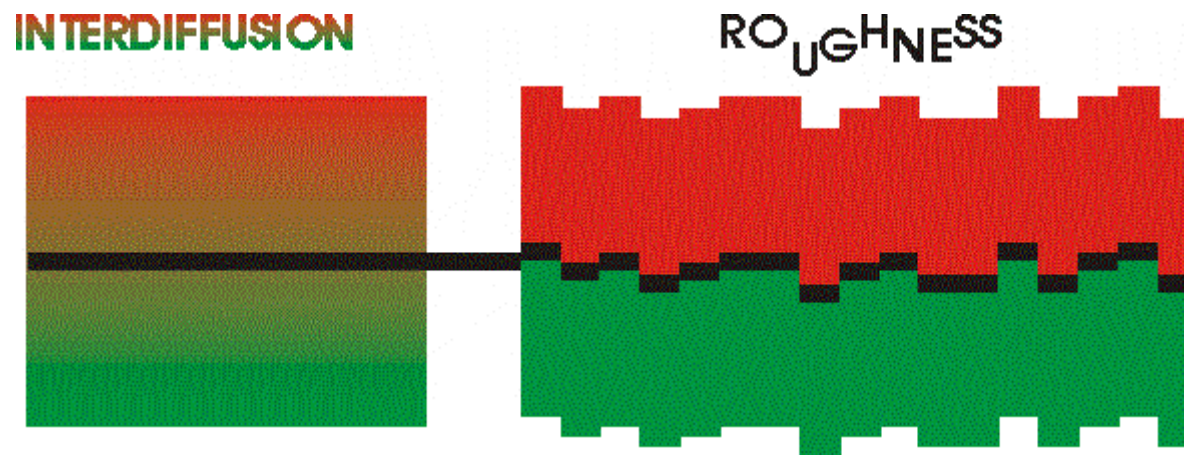


can be described by its amplitude and the lateral length scale

Epitaxial Fe/Cr superlattices on MgO(001) annealing

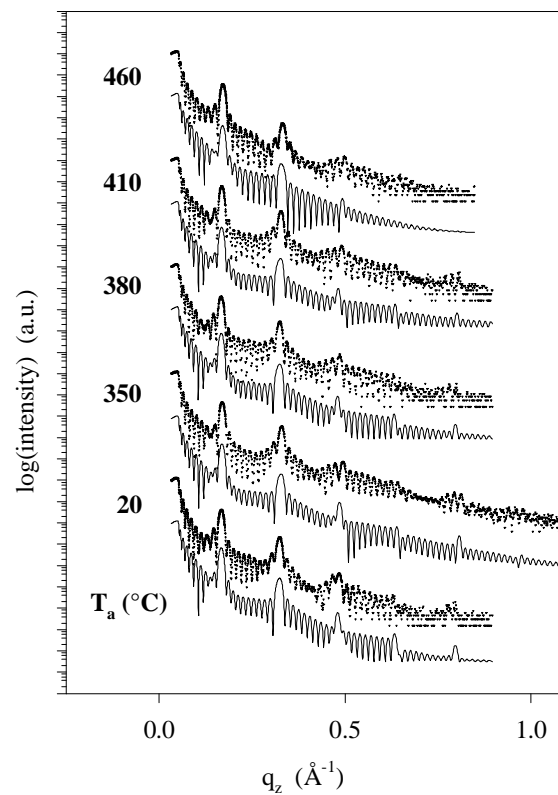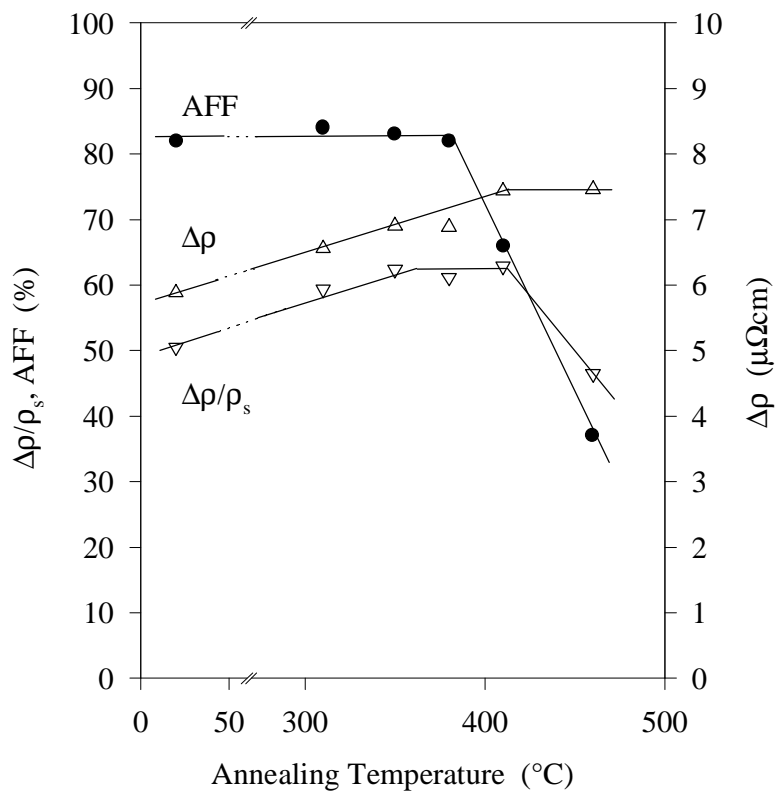


Phys. Rev. B 59, 1242 (1999)

Epitaxial Fe/Cr superlattices on MgO(001) annealing

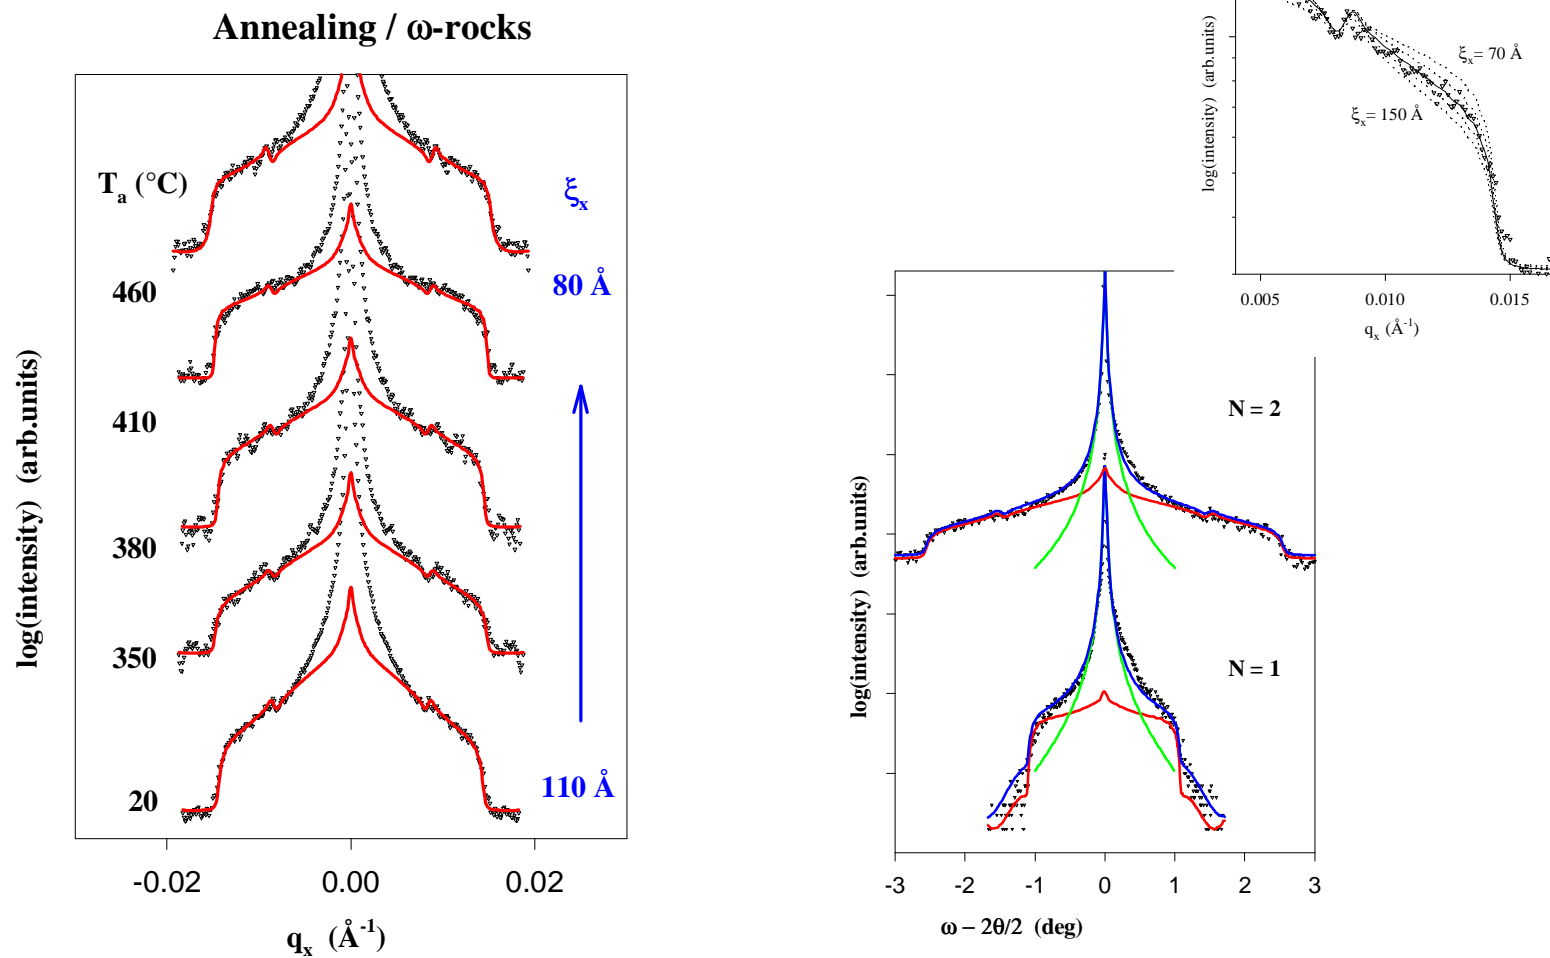

Phys. Rev. B 59, 1242 (1999)

Epitaxial Fe/Cr superlattices on MgO(001)

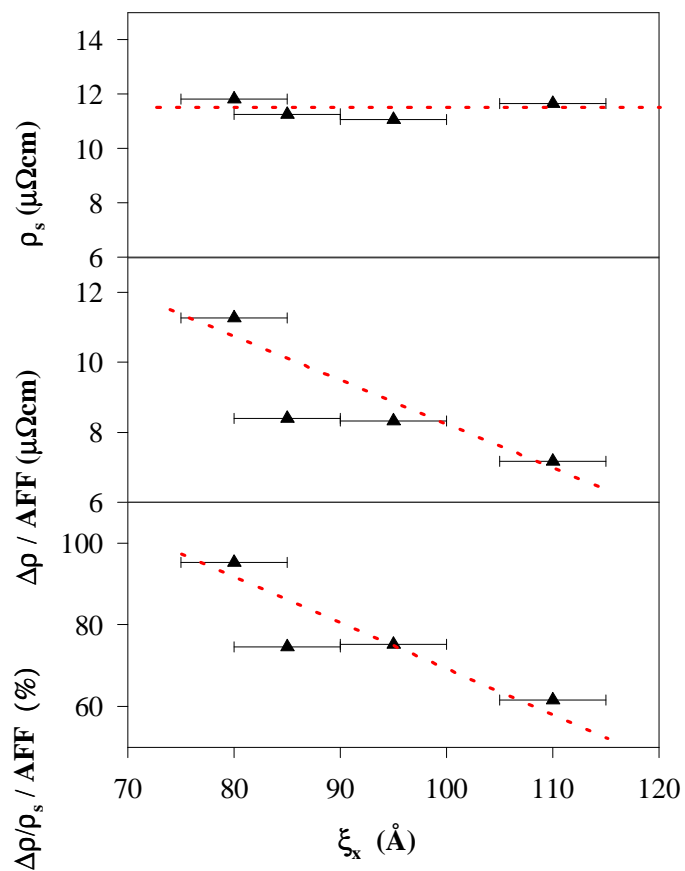


ρ_s is constant
[no interface scattering at saturation]

GMR is reduced with longer ξ

Phys. Rev. B 59, 1242 (1999)




–

Epitaxial Fe/Cr superlattices on MgO(001) Cr buffer layer

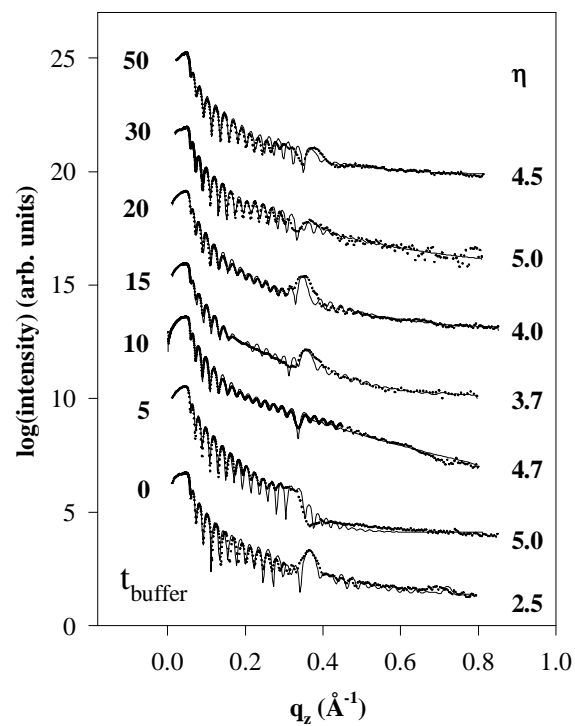


Europhys. Lett. 44, 379 (1998)

Epitaxial Fe/Cr superlattices on MgO(001) Cr buffer layer - Mößbauer Spectroscopy

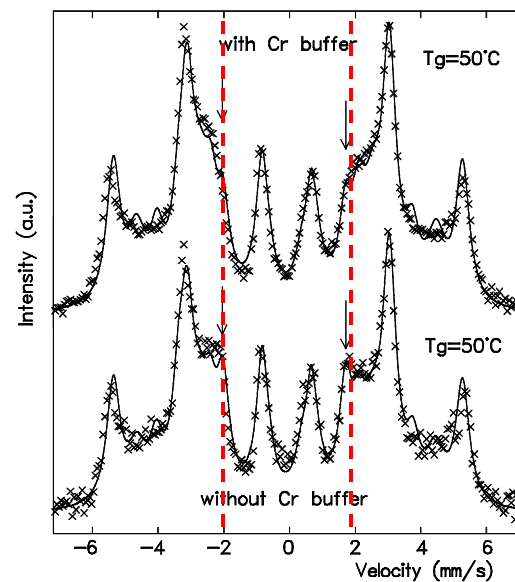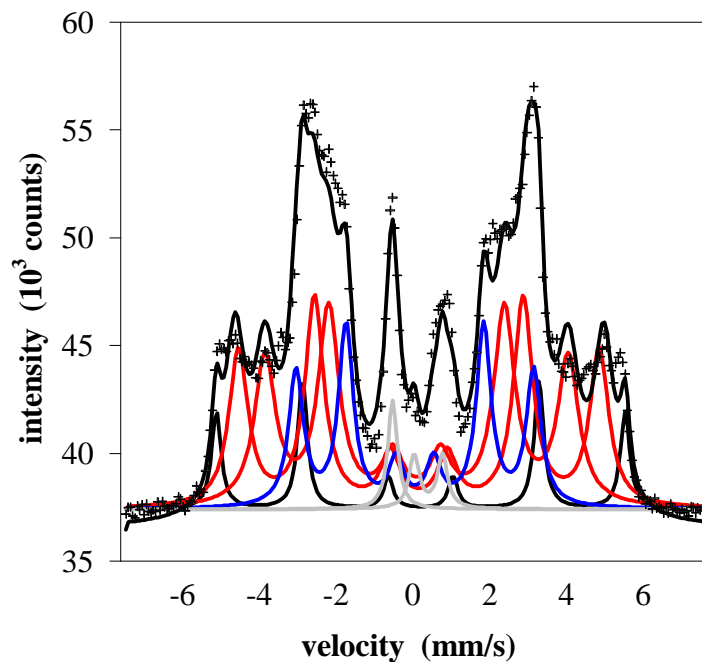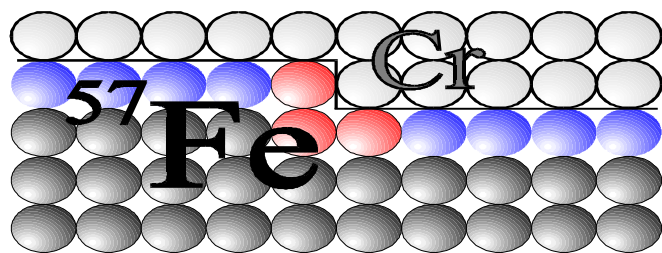

Europys. Lett. 44, 379 (1998)

Epitaxial Fe/Cr superlattices on MgO(001) Cr buffer layer

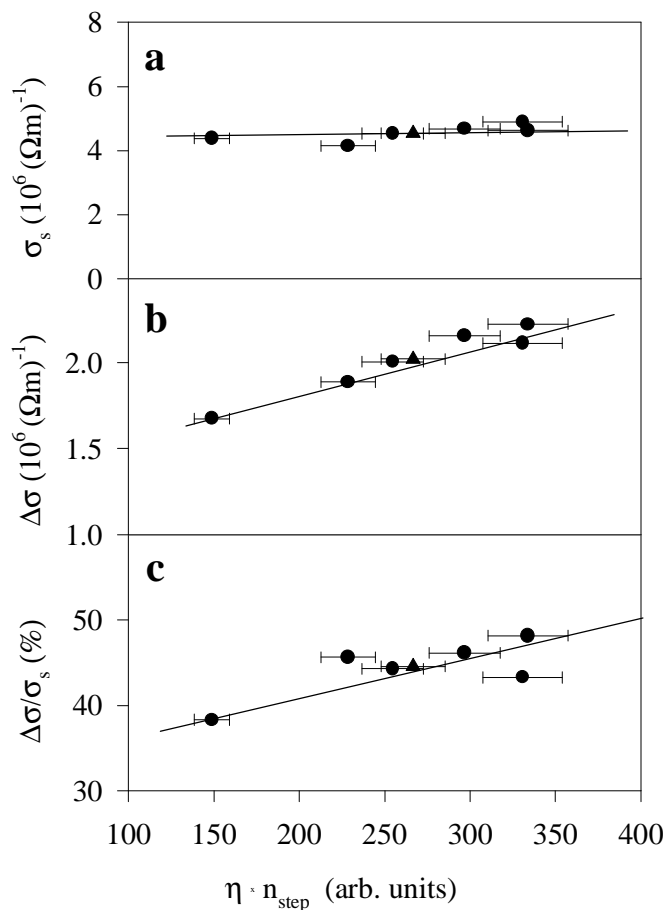


ρ_s is constant
[no interface scattering at saturation]

GMR is increased with increasing
roughness amplitude and step density

Europhys. Lett. 44, 379 (1998)


-

Epitaxial Fe/Cr superlattices on MgO(001) GMR

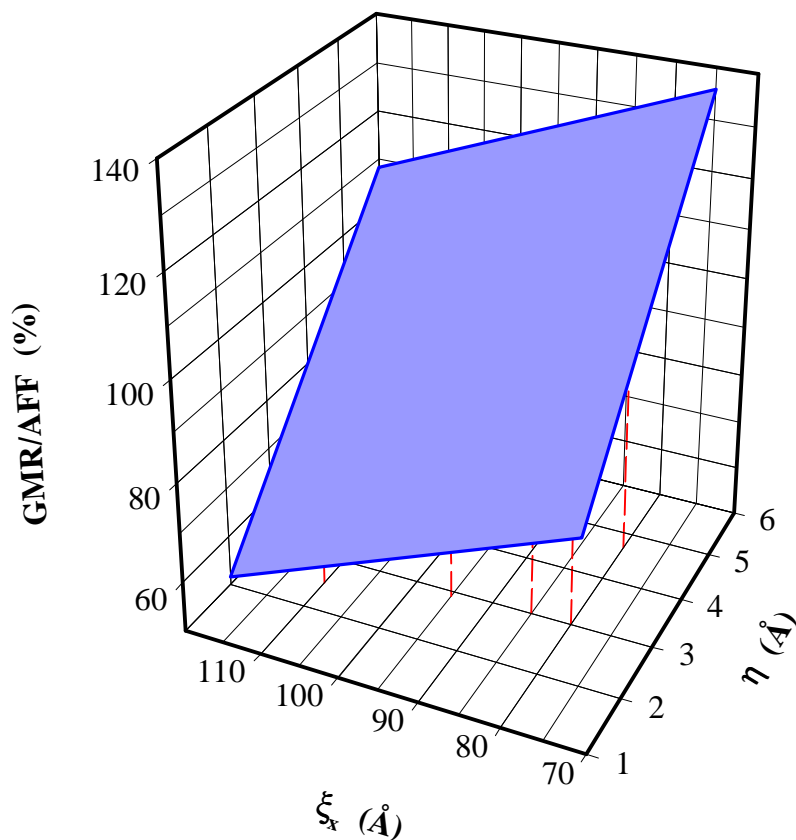


GMR is increased with
increasing roughness amplitude and
decreasing lateral correlation length

Epitaxial Fe/Cr superlattices on MgO(001)

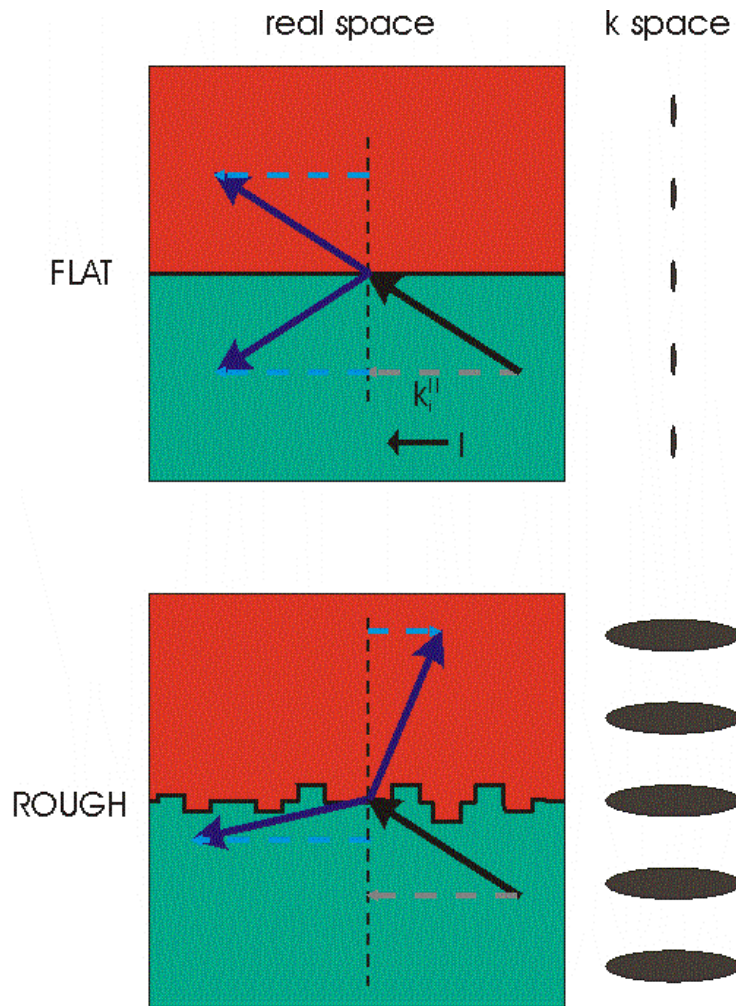


Epitaxial Fe/Cr superlattices on MgO(001)

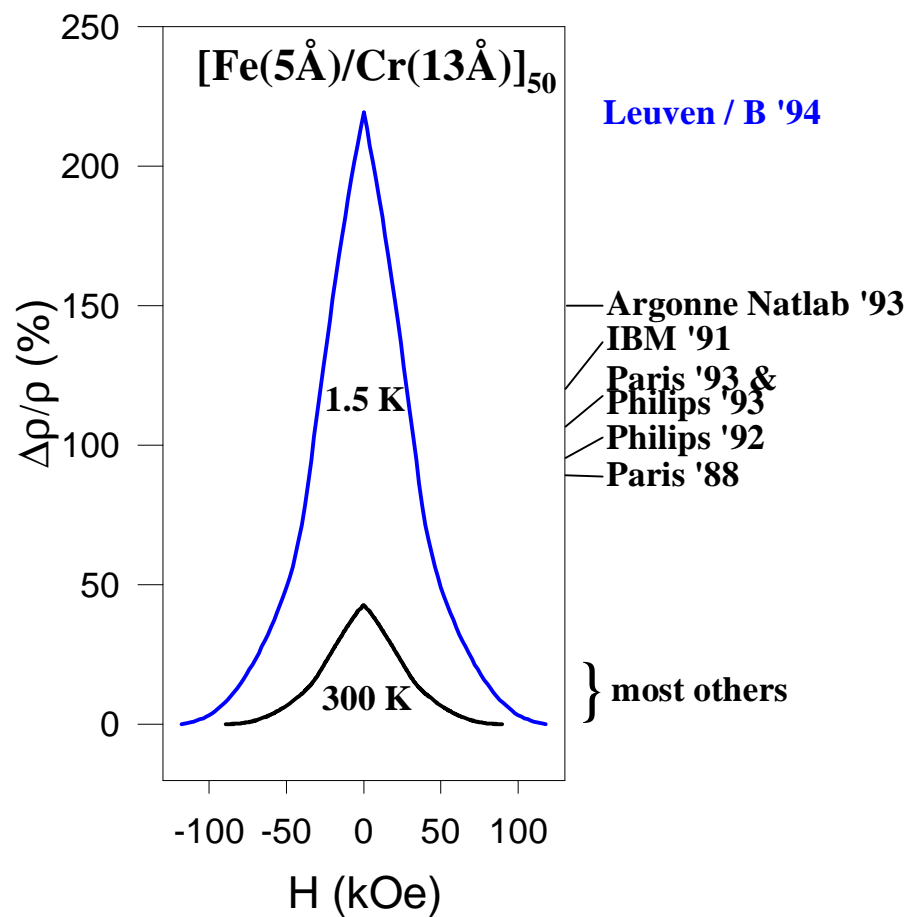

R. Schad et al. APL 64, 3500 (1994)

Polycrystalline Fe/Cr superlattices on YSZ GMR

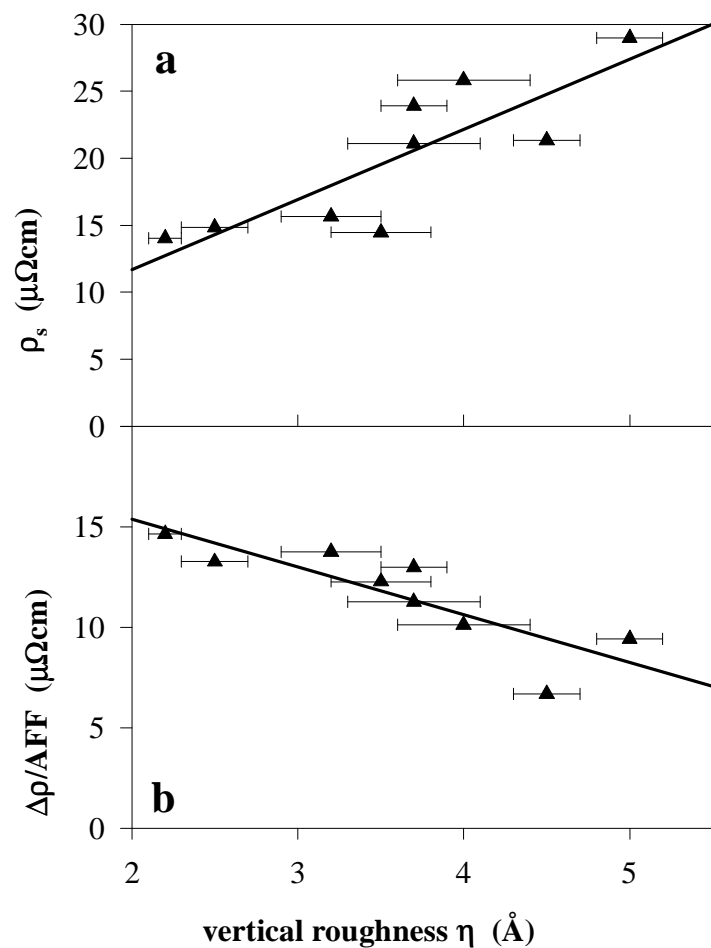

GMR dependence on interface roughness
is reversed for polycrystalline samples
=> importance of bulk scattering